

Comparative Study on the Corrosion Inhibition of Mild Steel by Aqueous Extract of Fenugreek Seeds and Leaves in Acidic Solutions

Ehteram A. Noor

Department of Chemistry, Girls' College of Education,
King Abd El Aziz University, Jeddah, Kingdom of Saudi Arabia

Abstract: Electrochemical impedance spectroscopy and potentiodynamic polarization measurements were used to study the effect of Aqueous Extract of Fenugreek Leaves (AEFL) and Aqueous Extract of Fenugreek Seeds (AEFS) on the corrosion of mild steel in HCl and H₂SO₄ solutions. In both acids, AEFL and AEFS act predominately as anodic type inhibitors. The inhibition efficiency of both AEFL and AEFS increases with increasing of their concentration in 2.0 M of both acids, but at certain concentration of both extracts it decreases with increasing concentration of both acids. However, in HCl solutions, the inhibition efficiency of both AEFL and AEFS was always greater than in H₂SO₄ solutions for otherwise identical conditions. In HCl solutions the adsorption of both AEFL and AEFS on mild steel surface obeys the Langmuir adsorption isotherm, while obeys the Temkin adsorption isotherm in H₂SO₄ solutions. It was found that the obtained results from EIS and PDP measurements are in good agreement. Good correlation between the inhibitor constituents and its inhibition efficiency in both acids was obtained and discussed.

Key words: Corrosion inhibition, aqueous extract, acidic solutions, AEFL, AEFS

INTRODUCTION

Corrosion of metals is a very common problem that has economic implications costing billions of dollars each year. Corrosion environment can be broadly classified as atmospheric, underground/soil waste, acidic, alkaline and combinations of these. A wide variety of acid or alkaline conditions are encountered in common environments. Many of the several corrosion problems encountered in the industries involves acids and in certain cases due to alkalis and solvents. Hence corrosion inhibition programs are now required in many industries such as oil and gas exploration and production, petroleum refining, chemical manufacturing and the product additive industries.

The corrosion inhibition is achieved by the addition of inhibitors to the system that prevent corrosion from taking place on metal surface. Inhibitors are chemicals that often work by adsorbing themselves on the metallic surface, protecting the metal surface by forming a film.

The scientific and technical corrosion literature has descriptions and lists of numerous chemical compounds that exhibit inhibitive properties for steel in acidic solutions, e.g. isothioronium iodides (Arab and Noor, 1992, 1993), quaternary ammonium salts of N-containing heterocyclics (Noor and Moubaraki, 2003; Noor, 2005), bipyrazolic derivatives (Tebbjji *et al.*, 2005), thiadiazoles derivatives (Lebrini *et al.*, 2005),

isoxazolidines (Ali *et al.*, 2005) and azoles (Popova, 2007). Of these only very few are actually used in practice. This is partly due to the fact that desirable properties of an inhibitor usually extend beyond those simply related to metal protection. Considerations of cost, toxicity, availability and environmental friendliness are of considerable importance.

Accordingly, the replacement of some toxic expensive chemical inhibitors by inhibitors obtained from natural sources is required to keep the environment more healthy, safely and under pollution control. Various natural products, e.g. Artemisia oil (Bouyanzer and Hammouti, 2004), Lawsonia extract (El-Etre *et al.*, 2005), Telfaria occidentalis extract (Oguzie, 2005), Ammi majus L. fruit extracts (Arab *et al.*, 2005), juice of Prunus cerasus (Ashassi-Sorkhabi and Seifzadeh, 2006), Pennyroyal oil from Mentha oulegium (Bouyanzer *et al.*, 2006), Occimum viridis extract (Oguzie, 2006) etc. have been reported to be good inhibitors for steel in acidic solutions.

Fenugreek is an annual plant (Fig. 1) widely cultivated for both medicinal and culinary uses. Several human intervention trials demonstrated that the antidiabetic effects of fenugreek seeds ameliorate most metabolic symptoms associated with type-1 and type-2 diabetes in both animals and humans models (Ribes *et al.*, 1986; Srinivas, 2005). In recent research, fenugreek seeds were experimentally shown to protect against cancers of



Fig. 1: The trifoliate fenugreek leaves and (b) the yellow rhombic fenugreek seed

the breast. So, as commonly eaten food, fenugreek is generally regarded as safe.

From the above point of view, the present work aimed to give comparative study by testing the Aqueous Extract of Fenugreek Leaves (AEFL) and Fenugreek Seeds (AEFS) as natural inhibitors for mild steel corrosion in 2.0 M solution of HCl and H₂SO₄ at 30° C by using Electrochemical Impedance Spectroscopy (EIS) and Potentiodynamic Polarization (PDP) measurements.

MATERIALS AND METHODS

Mild steel: The utilized mild steel has the following composition: C = 0.250%, Mn = 0.480, Si = 0.300, Ni = 0.040, Cr = 0.060, Mo = 0.020, S = 0.021, p = 0.019 and the rest up to 100% Fe.

Preparation of Fenugreek extracts: The dried leaves and seeds of Fenugreek were obtained from Indian productions. Stock solution of the inhibitor extract were prepared by boiling 10 g of dried, grounded fenugreek seeds or leaves in 250 mL of de-ionized water for 1 h. The extract was left all night and then filtered and completed to 250 mL by de-ionized water. Both the freshly prepared extract and that aged in a refrigerator for tow months give almost the same results.

Solutions: The aggressive solutions were prepared from analytical grade reagents (HCl and H₂SO₄) and de-ionized water. The required concentrations (0.5, 1.0, 2.0, 5.0 and 10.0% v/v) of AEFL and AEFS were prepared by diluting with 2.0 M of HCl and H₂SO₄ solutions. In all experiments, the temperature of solutions was controlled at 30°C using a water thermostat.

Electrochemical measurements: Electrochemical testing of inhibitors has the major benefit of short measurements time and giving vital information about the mechanism of

inhibition. The electrochemical cell is a conventional three-electrode Pyrex glass cell. The mild steel specimen was embedded in Teflon holder using epoxy resin with an exposed area of 0.785 cm². A platinum wire was used as an auxiliary electrode. The reference electrode was a Saturated Calomel Electrode (SCE) coupled to a Luggin capillary whose tip was located between the working electrode and the auxiliary electrode.

Electrochemical measurements were run by using a potentiostat/galvanostat (ACM Gill AC instrument model 655) and a personal computer were used. ACM Gill software was used for EIS and PDP analysis. Prior to each experiment, the working electrode was polished successively with different grade of emery papers, then the polished metal surface was rinsed with de-ionized water, ethanol and finally dipped in the tested solution. After 10 min of electrode immersion to attain open circuit potential, the electrochemical measurements will be done as follows:

Firstly, the EIS measurements were carried out using AC signals of amplitude 10 mV peak-to-peak at the open circuit potential in the frequency range of 10 KHz to 0.5 Hz. The charge transfer Resistance (R_{ct}) values have been calculated from the difference in the impedance at low and high frequencies. The capacitance of the double layer (C_{dl}) values are estimated from the frequency (f) at which the imaginary component of the impedance (-Z'') is maximum and obtained from the equation:

$$f(-Z''_{max.}) = \frac{1}{2\pi C_{dl} R_{ct}} \quad (1)$$

The percentage inhibition efficiency, IE(%), values from EIS measurements were calculated from R_{ct} data as follows:

$$IE_{R_{ct}} (\%) = \left(1 - \frac{R_{ct}^{-1}}{R_{ct^0}^{-1}}\right) \times 100 \quad (2)$$

Where, R_{ct⁰}⁻¹ and R_{ct}⁻¹ are the reciprocals of charge transfer resistance in absence and presence of inhibitor.

Secondly, for each experiment, after impedance spectrum was obtained the potentiodynamic current-potential curves will be recorded immediately by changing the electrode potential automatically from -550 to -350 with scan rate of 1 mV sG⁻¹. Tafel lines extrapolation method was used for detecting i_{corr} and E_{corr} values for the studied systems. Because of the presence of a degree of non-linearity in the part of the obtained polarization curves, the corresponding anodic and cathodic Tafel slopes (b_a and b_c) were calculated as a slope of the points after corrosion potential (i_{corr}) by ±50 mV using a computer

least square analysis. The IE (%) values from PDP measurements were calculated as follows:

$$IE_{i_{corr}} (\%) = \left(1 - \frac{i_{corr}}{i_{corr}^0}\right) \times 100 \quad (3)$$

Where, i_{corr}^0 and i_{corr} are the corrosion current densities in absence and presence of inhibitor.

All the electrochemical measurements were performed in stagnant, aerated solutions adjusted at 30°C.

RESULTS AND DISCUSSION

EIS measurements: Figure 2 and 3 show the Nyquist plots recorded for mild steel in 2.0 M of HCl and H₂SO₄, respectively, in the absence and presence of increasing concentrations of AEFL. Similar plots were obtained for mild steel in both acids in the presence of different concentrations of AEFS and not shown. In general, as

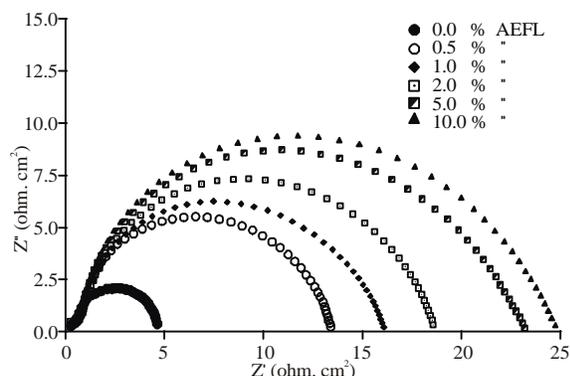


Fig. 2: Nyquist plots for mild steel in 2.0 M HCl in absence and presence of different concentrations of AEFL at 30°C

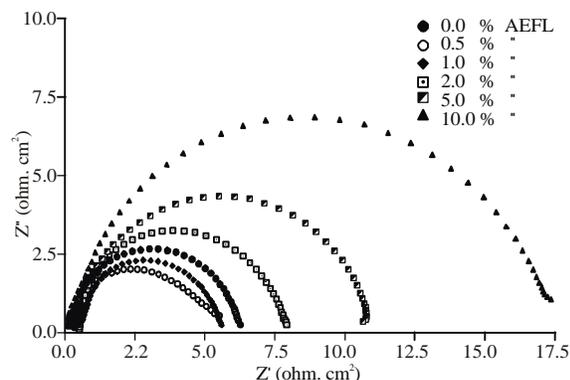


Fig. 3: Nyquist plots for mild steel in 2.0 M H₂SO₄ in absence and presence of different concentrations of AEFL at 30°C

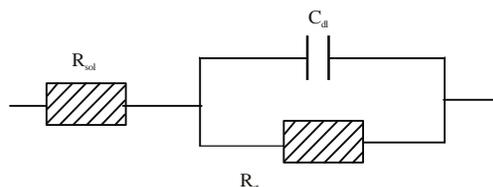


Fig. 4: The equivalent circuit model for the metal/solution interface

Table 1: EIS parameters and corresponding IE_{R_{ct}} (%) for mild steel corrosion in 2.0 M of HCl and H₂SO₄ in absence and presence of different concentrations of AEFL and AEFS

HCl		H ₂ SO ₄				
C _{inh} (v/v %)	R _{ct} (S cm ²)	C _{dl} (μF cm ²)	IE (%)	R _{ct} (S cm ²)	C _{dl} (μF cm ²)	IE (%)
AEFL						
0.0	4.33	1883.0	-	6.06	1706.0	-
0.5	13.41	745.5	67.71	4.90	7264.0	-23.67
1.0	16.23	737.8	73.32	5.09	2949.0	-19.06
2.0	18.84	657.1	77.02	7.73	1568.0	21.60
5.0	23.08	515.6	81.24	10.68	1028.0	43.26
10.0	24.56	487.8	82.37	17.71	546.1	65.78
AEFS						
0.5	13.47	741.6	67.85	6.41	1876.0	5.46
1.0	18.07	725.8	76.04	9.15	1704.0	33.77
2.0	18.98	623.3	77.19	10.33	979.0	41.34
5.0	24.92	439.5	82.62	13.41	827.6	54.81
10.0	28.61	372.9	84.87	16.68	667.9	63.67

impedance diagrams for solutions examined have almost a semicircular appearance, it indicates that the corrosion of steel is mainly controlled by a charge transfer process (Metikoš-Huković and Babić, 1998; Larabi and Harek, 2004; Bentiss *et al.*, 2005).

The impedance systems can be simulated by a simple circuit model of Randle type (Fig. 4) which consists of parallel combination of resistor, R_{ct} and a capacitor, C_{dl}, both are in series to resistor, R_{sol}. Randle equivalent circuit was successfully applied for some corrosion and corrosion inhibition systems (Zhao *et al.*, 2005; Dehri and Ozcan, 2006; Khaled, 2006). All the obtained EIS parameters (R_{ct} and C_{dl}) and the IE_{R_{ct}} for mild steel corrosion in both acids in absence and presence of different concentrations of AEFL and AEFS were recorded in Table 1. The results in this table can be illustrated as follows:

- In H₂SO₄ solutions, an acceleration behavior (R_{ct}^{inh.} < R_{ct}^{uninh.} and C_{dl}^{inh.} > C_{dl}^{uninh.}) is observed with the addition of low concentrations of AEFL (0.5 and 1.0 v/v%).
- In general, R_{ct} value increases and C_{dl} value decreases as the concentration of both extracts increases in both acids which indicates the adsorption of the inhibitor on the metal surface.

- Both extracts inhibit mild steel corrosion in 2.0 M HCl solution more than in H₂SO₄ solution. While in each acid AEFS inhibits mild steel corrosion more than AEFL.

PDP measurements: Figure 5 and 6 show the effect of AEFS on the anodic and cathodic polarization curves for mild steel in 2.0 M of HCl and H₂SO₄, respectively. Similar curves were obtained in the case of AEFL in both acids and not shown. It was observed that, in HCl and H₂SO₄, both extracts increase also both of the anodic and cathodic overpotentials but its influence on the cathodic side is much less obvious (i.e. act predominately as anodic inhibitors). All polarization parameters, that is, corrosion potential (E_{corr.}), Tafel slopes (b_c and b_a), corrosion current density (i_{corr.}) and the corresponding IE_{icorr.} (%) values for mild steel corrosion in both acids in absence and presence of different concentrations of both extracts were estimated and listed in Table 2 and the following observation could be drawn:

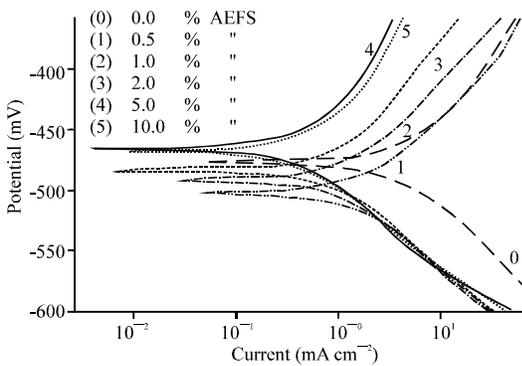


Fig. 5: PDP curves for mild steel in 2.0 M HCl in absence and presence of different concentrations of AEFS at 30 °C

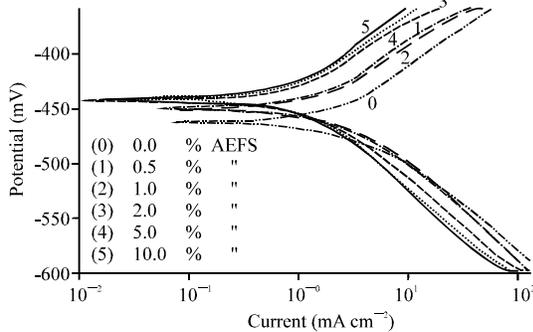


Fig. 6: PDP curves for mild steel in 2.0 M H₂SO₄ in absence and presence of different concentrations of AEFS at 30 °C

- The anodic (b_c) and cathodic (b_a) Tafel slopes do not change significantly in inhibited solution as compared to uninhibited solution. This observations suggest that both AEFL and AEFS adsorb on the metal surface by blocking the active sites of steel surface without affecting the mechanism of corrosion. This type of behaviour has been observed for mild steel in acid solutions containing Ammi majus L. fruit extracts (Arab *et al.*, 2005).
- The values of E_{corr.} change somewhat to less negative values with increasing extracts concentration in both acids.
- The IE_{icorr.} values are in good agreement with that obtained from EIS measurements.

Adsorption isotherm: Assuming that the corrosion inhibition were caused by the adsorption of the extract species on mild steel surface from both acids, the degree of surface coverage, θ , for different concentrations of both AEFL and AEFS in both acids was evaluated from EIS and PDP measurements by applying the ratio IE (%) / 100. Attempts were made to fit θ values to various adsorption isotherms and by far the best fit was obtained with the Langmuir isotherm (1917) for both AEFL and AEFS in HCl solutions and with Temkin (1941) isotherm for both extracts in H₂SO₄ solutions. According to Langmuir and Temkin isotherms, θ is related to inhibitor concentration, C_{inh}, via the following equations, respectively:

$$C_{inh} \cdot \theta^{-1} = \frac{1}{K_{e.c.a.}} + C_{inh} \quad (4)$$

$$\theta = \frac{1}{(-2a)} \ln K_{e.c.a.} + \frac{1}{(-2a)} \ln C_{inh} \quad (5)$$

Equation 4 and 5 predict a linear plot between values of C_{inh} · 10¹ and C_{inh} (Fig. 7) and between values of θ and C_{inh} (Fig. 8), respectively; where K_{ads} is the equilibrium constant of inhibitor adsorption and a is the Frumkin lateral interaction factor (Drazic *et al.*, 1994), describing the molecular interactions in the adsorbed layer and is a measure for the steepness of the adsorption isotherm. It can have both positive and negative values. The more positive the value of a, the steeper is the adsorption isotherm. It is well known that the standard free energy of adsorption, ΔG_{ads}° , is related to the equilibrium constant of adsorption, K_{ads} and ΔG_{ads}° can be calculated by the following equation:

$$\log K_{ads} = -\log C_{H_2O} - \frac{\Delta G_{ads}^{\circ}}{2.303RT} \quad (6)$$

Table 2: PDP parameters and corresponding IE_{corr} for mild steel corrosion in 2.0 M of HCl and H_2SO_4 in absence and presence of different concentrations of AEFL and AEFS

C_{inh} (v/v %)	HCl					H_2SO_4				
	$-E_{corr}$ (mV)	$-b_c$ (mV)	b_a (mV)	I_{corr} (mA cm ⁻²)	IE (%)	$-E_{corr}$ (mV)	$-b_c$ (mV)	b_a (mV)	I_{corr} (mA cm ⁻²)	IE (%)
AEFL										
0.0	478	65	73	6.04	-	462	51	60	4.30	-
0.5	480	64	70	2.82	53.31	450	47	55	5.46	-26.98
1.0	467	61	71	1.76	70.86	443	46	52	5.32	-23.72
2.0	467	63	74	1.57	74.01	439	45	51	3.70	13.95
5.0	466	64	73	1.06	82.45	437	47	47	2.52	41.40
10.0	465	65	70	0.77	87.25	437	45	47	1.84	57.21
AEFS										
0.0	478	65	73	6.04	-	462	51	60	4.30	-
0.5	503	61	71	1.92	68.21	450	42	53	3.82	11.16
1.0	490	65	73	1.36	77.48	448	43	46	3.01	30.00
2.0	485	51	65	1.33	77.98	442	43	49	2.61	39.30
5.0	466	56	65	1.03	82.95	441	41	46	1.94	54.88
10.0	468	58	62	0.74	87.75	439	39	44	1.40	67.44

Table 3: Langmuir adsorption isotherm parameters for AEFL and AEFS onto mild steel in HCl at 30°C

C_{inh} v/v %	Adsorption parameters					
	Slope		$K_{e.c.a}$ (ml ⁻¹ l)		ΔG_{ads}° KJ mol ⁻¹	
	EIS	PDP	EIS	PDP	EIS	PDP
AEFL	1.20	1.12	0.506	0.290	-15.69	-14.29
AEFS	1.20	1.12	0.526	0.408	-15.79	-15.15

Table 4: Temkin adsorption isotherm parameters for AEFL and AEFS onto mild steel in H_2SO_4 at 30°C

C_{inh} v/v %	Adsorption parameters					
	a		$K_{e.c.a}$ (ml ⁻¹ l)		ΔG_{ads}° KJ mol ⁻¹	
	EIS	PDP	EIS	PDP	EIS	PDP
AEFL	-1.58	-1.62	0.080	0.068	-11.04	-10.62
AEFS	-2.79	-2.78	0.421	0.389	-15.23	-15.03

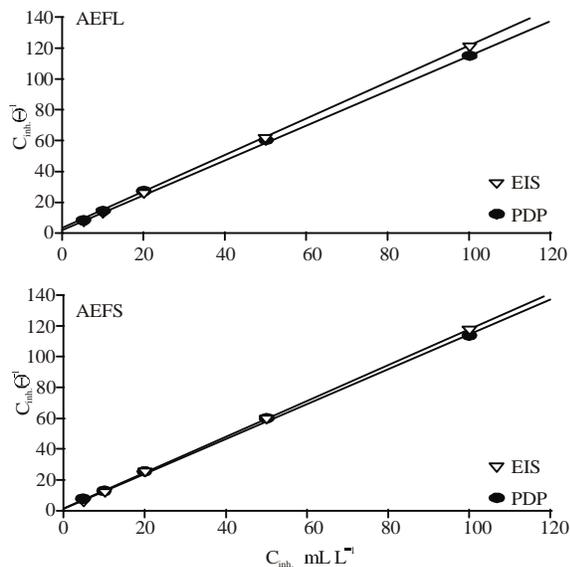


Fig. 7: Langmuir isotherm for adsorption of AEFL and AEFS on mild steel surface in 2.0M HCl at 30°C

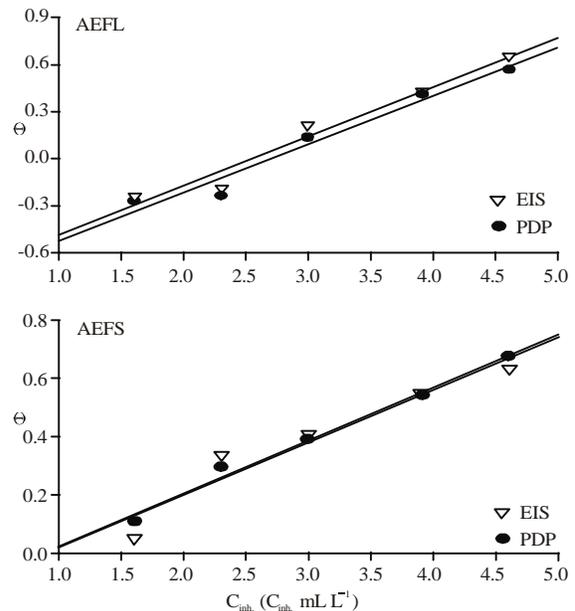


Fig. 8: Temkin isotherm for adsorption of AEFL and AEFS on mild steel surface in 2.0M H_2SO_4 at 30°C

Where, C_{H_2O} is the concentration of water molecules at metal electrolyte interface in mL LG¹.

All adsorption parameters obtained for the adsorption of both AEFL and AEFS on mild steel surface from HCl and H_2SO_4 at 30EC were recorded in Table 3 and 4, respectively. Inspection of Table 3 and 4, the following results can be obtained:

- C The negative values of a factor indicates the existence of repulsive forces among the adsorbed species on mild steel from H_2SO_4 solutions emphasizing the lower inhibitive properties of both AEFL and AEFS in such solutions as compared to that detected in HCl solutions.

- The negative values of $\Delta G_{\text{ads}}^{\circ}$ indicate spontaneous interaction of inhibitor species with the corroding mild steel surface.
- From $\Delta G_{\text{ads}}^{\circ}$ values, both AEFL and AEFS have better performance in HCl solutions than in H₂SO₄. On the other hand, AEFS is more effective corrosion inhibitor than AEFL in both acids.

Inhibitor constituents and inhibition mechanism:

The active constituents in Fenugreek plant are (<http://www.fenugreek-seeds.com/>).

Alkaloides: Trime thylamine, Neurin, Trigonelline (N-methyl-pyridinium-3-carboxylate), Choline (trimethyl ethanolamine), Gentianine, Carpaine and Betain.

Amino acids: Isoleucine; 4-hydroxyisoleucine, histidine, leucine, L-tryptophan, alanine and argenine.

Saponins: Graecunins, fenugrin B, fenugreekine and trigofenosides A-G.

Seroidal saponogens: Yamogenin, diosgenin, smilagenin, sarsasapogenin, tigogenin, neotigogenin, gitogenin, neogitogenin and yuccagenin.

Fiber: Gum and neutral detergent.

Others: Coumarin, lipids, vitamins and minerals.

Most of the above substances are concentrated in seeds part more than the other parts (<http://www.swsbm.com/Constituents/constituentsQ-Z.html>), explaining why AEFS has good inhibitory action as compared with AEFL. As noticed, fenugreek plant contains a wide variety of N-containing compounds (e.g. amines, amino acids, quaternary ammonium of N-heterocyclic compounds, etc.) which may play an important role in interpretation the obtained results. It was reported (Schmitt, 1984) that as a rule of thumb, N-containing compounds such as amines, amino acids and quaternary ammonium salts exert their best efficiencies in prevention corrosion of iron and steel in HCl solutions while they are relatively ineffective in H₂SO₄ and this behaviour is in good agreement with the obtained results in the present research.

As known, in aqueous acidic solutions amines exist either as neutral molecules or in the form of onium ions. The possibility of cation adsorption by electrostatic forces is determined by the electric charge of the electrode with respect to the solution, i.e., by the Potential of Zero Charge (PZC) with respect to E_{corr} . This model defines the N-potential (Banerjee and Malhotra, 1992), which is expressed as:

$$\phi = E_{\text{corr}} - p.z.c. \quad (8)$$

There are some evidence (Banerjee and Malhotra, 1992; Lebrini *et al.*, 2005) revealed that mild steel surface is positively charged in acid solutions (i.e. positive value for N potential). So, direct adsorption of onium ions on the positively charged metal surface is not favorable. Accordingly the extent of onium ions adsorption depends on the nature of the anions in acidic solutions. Chloride ions of smaller size and having no primary hydration sheaths are more strongly adsorbed on the positively charged metal surface than the heavily hydrated ions of sulphate (Muralidharan *et al.*, 1994). This results in a change from a positive to a negative charge, thus increasing the electrostatic component of the energy of adsorption. So a close-backed inhibitor film will form on the metal surface and inhibit iron ions to enter the solution. Similarly lesser adsorption of sulphate ions on the metal surface leads to lesser inhibition of corrosion and in some cases of low inhibitor concentration may lead to accelerate corrosion rate. An acceleration behavior was reported for mild steel in H₂SO₄ in the presence of some amino phenols and this behavior tends to decrease with the increase in the inhibitor concentration, while they behave very well as corrosion inhibitors in HCl solutions (Rengamani *et al.*, 1994). These observations are similar to that obtained in the present research.

Moreover, it was reported (Muralidharan *et al.*, 1994) that organic amine-type inhibitors can act in acidic solutions in two different ways:

- C It can compete with the anions of the acid (Cl^- or SO_4^{2-}) for position on the water-covered metal surface. In doing so the protonated amine loses its protons on entering the double layer and gets chemisorbed by donating a pair of electrons to the metal.
- C Protonated amines can be electrostatically adsorbed on the anions-covered metal surface through its hydrogen ions.

Both these mechanisms can increase the inhibitor performance depending on the type of anions in the acidic solution. To elucidate these mechanisms further studies must be done such as studying the effect of temperature and halide ion addition on the performance of fenugreek extract.

Effect of acid concentration: The effect of different acid molarities (1 M-5.5 M) on the inhibitive efficiency (IE_{R_t} (%)) of AEFL and AEFS at concentration level of

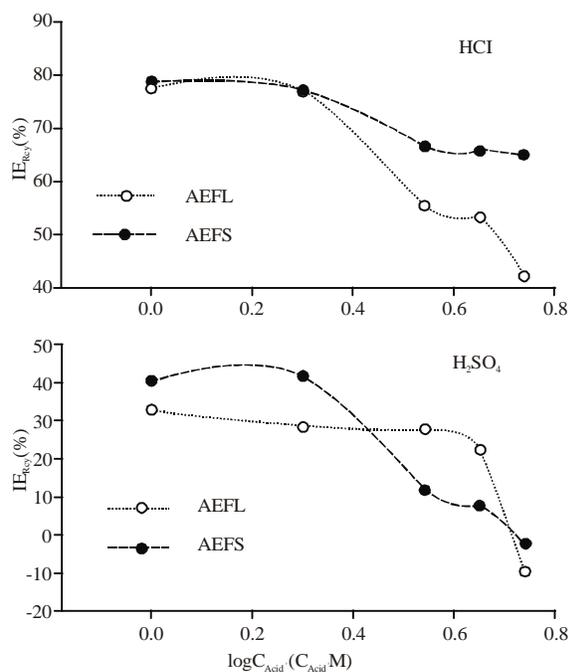


Fig. 9: Effect of acid concentration on inhibition efficiency of 2.0 v/v% AEFL and AEFS for mild steel at 30°C

2.0 v/v% is shown in Fig. 9. It may be generalized that the inhibition efficiency of both extracts decreases with increasing the concentration of both acids and this behaviour is more pronounced in the case of H₂SO₄ solutions. This behavior may be traced to the increase tendency of the metal to react with acid and liberate hydrogen vigorously (Talati and Gandhi, 1983). This may not allow the establishment of adsorption process sufficiently and rapidly resulting in decrease of inhibition. However, at all the studied acid concentrations the AEFL and AEFS inhibit mild steel corrosion in HCl solutions greater than in H₂SO₄ solutions.

CONCLUSION

- C In HCl and H₂SO₄ solutions, both AEFL and AEFS act predominately as anodic type inhibitors.
- C The inhibition efficiency of both AEFL and AEFS increases with increasing of their concentration in 2.0 M of both acids, but at certain concentration of both extracts it decreases with increasing concentration of both acids.
- C In HCl solutions, the inhibition efficiency of both AEFL and AEFS was always greater than in H₂SO₄ solutions for otherwise identical conditions.
- C The adsorption of both AEFL and AEFS on mild steel surface in HCl solutions obeys the Langmuir adsorption isotherm, while obeys the Temkin adsorption isotherm in H₂SO₄ solutions.

- C The obtained results from EIS and PDP measurements are in good agreement.
- C Good correlation between the inhibitor constituents and its inhibition efficiency in both acids was obtained and discussed.

REFERENCES

- Ali, S.A., A.M. El-Shareef, R.F. Al-Ghamdi and M.T. Saeed, 2005. The isoxazolidines: The effect of steric factor and hydrophobic chain length on the corrosion inhibition of mild steel in acidic medium. *Corros. Sci.*, 47: 2659-2678.
- Arab, S.T. and A.M. Al-Turkustani and S.Y. Al-Nami, 2005. Utilization of L. Ammi Majus fruit extracts as inhibitors for mild steel corrosion in acid media. *Mater. Sci. Res. Ind.*, 3: 99-110.
- Arab, S.T. and E.A. Noor, 1992. Effect of Some S-Alkylisothiuronium Iodides on the Corrosion of Steel in 1.0M Hydrochloric Acid. *Int. J. Chem.*, 3: 211.
- Arab, S.T. and E.A. Noor, 1993. Inhibition of Acid Corrosion of Steel by Some S-Alkylisothiuronium Iodides. *Corrosion (NACE)*, 49: 122.
- Ashassi-Sorkhabi, H. and D. Seifzadeh, 2006. The inhibition of steel corrosion in hydrochloric acid solution by juice of Prunus cerasus. *Int. J. Electrochem. Sci.*, 1: 92-98.
- Banerjee, G., S.N. Malhotra, 1992. Contribution to adsorption of aromatic amines on mild steel surface from HCl solutions by impedance. UV and Raman spectroscopy. *Corrosion*, 48: 10-15.
- Bentiss, F., M. Lebrini and M. Lagrene, 2005. Thermodynamic characterization of metal dissolution and inhibitor adsorption processes in mild steel/2,5-bis(n-thienyl)-1,3,4-thiadiazoles/hydrochloric acid system. *Corros. Sci.*, 47: 2915-2931.
- Bouyanzer, A., B. Hammouti, 2004. A study of anti-corrosive effects of Artemisia oil on steel. *Pigment and Resin Technol.*, 33: 287-292.
- Bouyanzer, A., B. Hammouti, L. Maida, 2006. Pennyroyal oil from Mentha pulegium as corrosion inhibitor for steel in 1 M HCl. *Mater. Lett.*, 60: 2840-2843.
- Dehri, I. and M. Ozcan, 2006. The effect of temperature on the corrosion of mild steel in acidic media in the presence of some sulphur-containing organic compounds. *Mater. Chem. Phys.*, 98: 316-323.
- Drazic, D.M., L.J. Vracar and V.J. Drazic, 1994. The kinetics of inhibitor adsorption on iron. *Electrochim. Acta*, 39: 1165-1170.
- El-Etre, A.Y., M. Abdallah and Z.E. El-Tantawy, 2005. Corrosion inhibition of some metals using lawsonia extract. <http://www.fenugreek-seeds.com/http://www.swsbm.com/Constituents/constituentsQ-Z.html>. *Corros. Sci.*, 47: 385-395.

- Khaled, K.F., 2006. Experimental and theoretical study for corrosion inhibition of mild steel in hydrochloric acid solution by some new hydrazine carbodithioic acid derivatives. *Applied Surf. Sci.*, 252: 4120-4128.
- Langmuir, I, 1917. The Constitution and Fundamental properties of solid and Liquids. II. Liquids. *J. Am. Chem. Soc.*, 39: 1848-1906.
- Larabi L. and Y. Harek, 2004. Effect of Iodide Ions on Corrosion Inhibition of Mild Steel in 0.5 M H₂SO₄ by Poly (4-Vinylpyridine), *Portug. Electrochi. Acta*, 22: 227-247.
- Lebrini, M., M. Lagrenee, H. Vezin, L. Gengembre and F. Bentiss, 2005. Electrochemical and quantum chemical studies of new thiadiazole derivatives adsorption on mild steel in normal hydrochloric acid medium. *Corros. Sci.*, 47: 485-505.
- Metikoš-Hukoviã, M. and R. Babia, 1998. Corrosion protection of aluminium in acidic chloride solutions with nontoxic inhibitors. *J. Applied Electrochem.*, 28: 433-439.
- Muralidharan, S., P. Chandrakumari, K. Madhavan, T. Vasudevan and S. V. Iyer, 1994. N-Octylamine as the inhibitor for the corrosion of mild steel in acidic solutions. *Anti-Corros. Meth. Mater.*, 41: 4-8.
- Noor, E.A., 2005. The inhibition of mild steel corrosion in phosphoric acid solutions by some N-heterocyclic compounds in the salt form. *Corros. Sci.*, 47: 33-55.
- Noor, E.A. and A.H. Al Moubaraki, 2003. Some factors affecting the corrosion inhibition of mild steel in HCl solutions (I) effect of inhibitor concentration. *Int. J. Chem.*, 13: 139-156.
- Oguzie, E.E., 2005. Inhibition of mild steel by *Telfaria occidentalis* extract. *Pigment and Resin Technol.*, 34: 321-326.
- Oguzie, E.E., 2006. Studies on the inhibitive effect of *Occimum viridits* extract on the acid corrosion of mild steel. *Mater. Chem. Phys.*, 99: 441-446.
- Popova, A., 2007. Temperature effect on mild steel corrosion in acid media in presence of azoles. *Corros. Sci.*, 49: 2144-2158.
- Rengamani, S., S. Muralidharan, M.A. Kulandainathan and S.V. Iyer, 1994. Inhibiting and accelerating effects of aminophenols on the corrosion and permeation of hydrogen through mild steel in acidic solutions. *J. Applied Electrochem.*, 24: 355-360.
- Ribes, G., Y. Sauvaire, C. Da Costa, 1986. Antidiabetic effects of subfractions from fenugreek seeds in diabetic dogs. *Proc. Soc. Exp. Bio. Med.*, 182:159-166.
- Schmitt, G., 1984. Application of corrosion inhibitors for acid media. *Br. Corros. J.*, 19: 165.
- Srinivasan, K., 2005. Plant foods in the management of diabetes mellitus: Spices as beneficial antidiabetic food adjuncts. *Int. J. Food Sci. Nutr.*, 56: 399-414.
- Talati, J.D. and D.K. Gandhi, 1983. N-heterocyclic compounds as corrosion inhibitors for aluminium-copper alloy in hydrochloric acid. *Corros. Sci.*, 23: 1315-1332.
- Tebbjji, K., B. Hammouti, H. Oudda, A. Ramdani and M. Benkadour, 2005. The inhibitive effect of bipyrazolic derivatives on the corrosion of steel in hydrochloric acid solution. *Applied Surf. Sci.*, 252: 1378-1385.
- Temkin, M.I., 1941. *Zh. Fiz. Khim.*, 15: 296.
- Zhao, P., Q.C. Liang and Y. Li, 2005. Electrochemical, SEM/EDS and quantum chemical study of phthalocyanines as corrosion inhibitors for mild steel in 1 mol/l HCl. *Applied Surf. Sci.*, 252: 1596-1607.